

Impregnation of Chitosan onto Activated Carbon for High Adsorption Selectivity towards CO₂: CO₂ Capture from Biohydrogen, Biogas and Flue Gas

Chantaraporn Phalakornkule^{1,2,*}, Jarint Fongchuen^{1,2} and Totsaphol Pitakchon^{1,2}

¹Department of Chemical Engineering, King Mongkut's University of Technology North Bangkok, Bangkok, Thailand

²The Research and Technology Center for Renewable Products and Energy, King Mongkut's University of Technology North Bangkok, Bangkok, Thailand

*Corresponding Author: cphalak21@yahoo.com; cpk@kmutnb.ac.th

Abstract: In this study, a novel bio-based adsorbent was developed for CO₂ adsorption. Palm shell activated carbons were immersed in chitosan solutions at the concentrations between 0.1-2 g/L under agitation. A series of chitosan impregnated activated carbon was obtained: 0.12-0.98 wt% chitosan. The chitosan impregnated activated carbon that was the most suitable for CO₂/H₂ separation was the one impregnated with 0.1 g/L chitosan solution yielding 0.12 g chitosan per one hundred gram activated carbon. A lab-scale pressure swing adsorption process using the modified activated carbon as the adsorbent (adsorption pressure of 4 bar and the feed flowrate of 2 L/min 50-50 mixture of H₂ and CO₂ for a period of 2 min) yielded ultra pure H₂ for 8 cycles before the breakthrough of CO₂, while only 3 cycles were achieved with the native activated carbon. The chitosan impregnated activated carbon that was the most suitable for CO₂/CH₄ separation was the one impregnated with 2 g/L chitosan solution yielding 0.76 g chitosan per one hundred gram activated carbon. The lab-scale adsorption process using the modified activated carbon as the adsorbent yielded ultra pure CH₄ for 3 cycles before the breakthrough of CO₂, while only 1 cycle was achieved with the native activated carbon. For the CO₂/N₂ dynamic adsorption of 0.12 wt% CHI/AC, 100% nitrogen was achieved for 1-8 cycles. For the CO₂/N₂ dynamic adsorption of 0.76 wt% CHI/AC, 100% nitrogen was achieved for 1-9 cycles.

Keywords: Modified activated carbon, chitosan, impregnation, biohydrogen, biogas, flue gas, purification.

1. Introduction

Nowadays, our world is facing both energy and environmental problems which affect the people's living quality and a nation's economics. Carbon dioxide (CO₂), a green house gas that is released when burning fossil fuels, has been realized to play a crucial role in climate change [1]. The rising level of CO₂ can gravely affect our future. In contrast to petroleum based energy, renewable energy produced from biomass has received a special attention in recent years because it only releases the amount of atmospheric CO₂ that was stored in the plant during its growth. Two of the important renewable energy produced from biomass by anaerobic digestion are biogas and biohydrogen. Utilization of biogas and biohydrogen reduces CO₂ emissions and helps to avoid an increase of the CO₂ concentration in the atmosphere. Furthermore, CO₂ separation from biogas and biohydrogen following by a conversion of CO₂ to other forms or by CO₂ capture and storage can be a strategy for decreasing the CO₂ concentration in the atmosphere.

There are a number of techniques for gas separation such as absorption, adsorption and membrane. Evaluation of upgrading techniques for biogas are available and it has been reported that adsorption is a potential technology for CO₂ removal from biogas especially for small and middle sized upgrading plants [2]. The active part in the adsorption process is the adsorbent. There is a variety of adsorbents such as zeolite, silica gel, activated alumina and activated carbon. Activated carbon offers an attractive and inexpensive adsorbent for removing several solutes from aqueous solutions as well as from gaseous environment. In recent years, interest has been growing in the use of low-cost and abundantly available lignocellulosic materials as precursors for the preparation of activated carbon. The nature of the final product depends on both the starting material and the activation procedure. The activated carbons may differ mainly in pore size distribution and surface polarity [3].

A further development of activated carbon is to modify

the pore size and/or to control the pore size distribution. Another development of activated carbon is to modify its surface polarity in order to enhance selective chelating ability. The selection is based on the chemical interactions which can preferentially attract polar molecules onto the carbons. This type of activated carbon can be prepared by oxidizing the activated carbon with acids and bases [4] such as nitric acid [5], tannic acid [6], citric acid [7], ammonia [8] or by microwave, ozone and plasma treatment [4,9]. To a lesser extent, the surface polarity can be changed by coating an adsorbent with polymers such as polyethyleneimine [4,10-12]. Yin et al. (2007) [9] impregnated palm shell activated carbon with low and high molecular weight polyethyleneimine (PEI). The impregnation with low molecular weight PEI was found to enhance Cd²⁺ adsorption capacity of the activated carbon. For a gas separation application, the palm shell activated carbon impregnated with 0.26 wt% PEI was found to have higher adsorption selectivity towards CO₂ [13].

In our viewpoint, the activated carbon with modified surface polarity can be prepared with local resource and environmentally friendly materials with similar effectiveness. One attractive alternative is chitosan biopolymer or poly [β-(1→4)-2-amino-2-deoxy-D-glucopyranose], which is mainly produced by alkaline deacetylation of chitin [14-16]. The structure of chitin and chitosan is similar to cellulose except that the C-2-hydroxyl group of cellulose is replaced by an acetamido and amino group, respectively (Figs. 1(a)-(c)). Chitosan is insoluble in most organic solvents but it dissolves in acidic solutions [17].

In this study, modified activated carbon is prepared by impregnating chitosan onto activated carbons. The modified activated carbon was produced at chitosan weight percentages of 0.12, 0.25, 0.36, 0.66, 0.76 and 0.98 wt%. The dynamic CO₂ adsorptions of the modified activated carbon were determined using a lab-scale adsorption column and the results were compared with those of the native activated carbon. In addition, an evaluation of carbon capture and storage by the modified activated carbon is discussed.

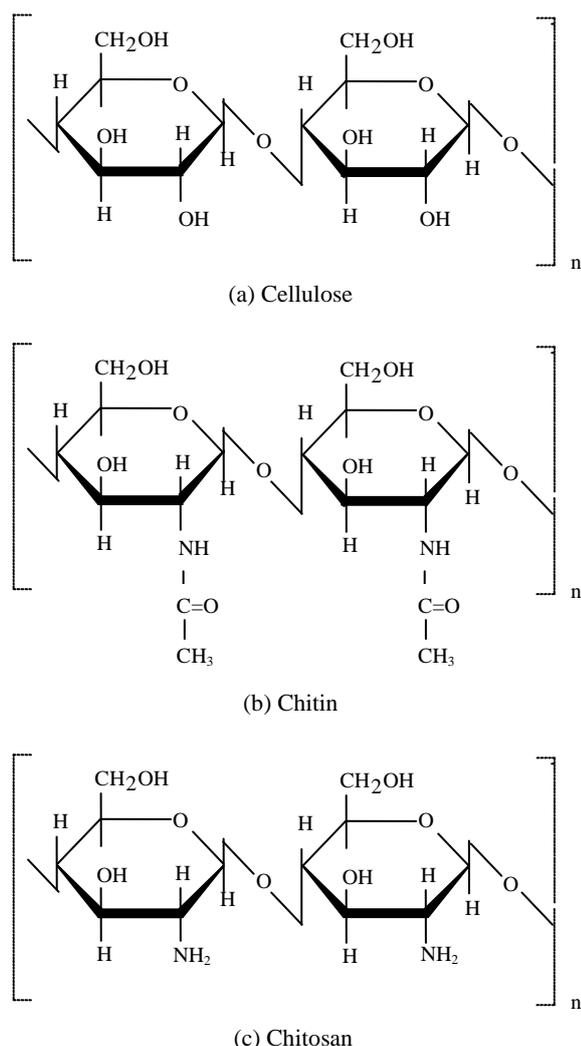


Figure 1. Structures of (a) cellulose (b) chitin and (c) chitosan.

2. Experimental

2.1 Materials

Palm shell activated carbon produced by physical activation process with steam as the activating agent was obtained from C. Gigantic Carbon Co., Ltd. (Thailand). The characteristics of the activated carbon are as follow: bulk density 0.59 g/mL, particle size distribution 91% 200 mesh pass, iodine absorption 862 mg/g, pH 10.1 and ash content 6.1%.

Gases CO_2 , CH_4 and N_2 , were of analytical grades (99.995%). The chitosan was provided by Taming Enterprises Co., Ltd. (Thailand) and its characteristics are as follows: degree of deacetylation = 93.8%; molecular weight = 17,010 dalton; moisture content = 7%; ash content = 0.95%; protein content = 3.01%; viscosity = 27.40×10^{-3} Pa·s. Chitosan solution (2% w/v) was prepared by mixing 2 g of chitosan in 900 mL of 1 M acetic acid. The solution was mixed at 200 rpm for 24 h. One hundred mL of 1M sodium acetate was added and agitated for 1 h.

2.2 Chitosan impregnation onto activated carbon

The activated carbons were washed with deionized water to remove fines and dirt and then oven dried at 378 K for 24 h before the impregnation process was conducted. The AC was sieved to sizes ranging from 3-4 mm and divided in 2 g portions and placed in separate Erlenmeyer flasks. Fifty mL of chitosan solutions with initial concentrations of 0.1-2.0 g/L

were added. The AC together with the chitosan solution was then agitated in an orbital shaker at 180 rpm at 298 K for 3 days.

The AC was separated from the chitosan solution by filtration. Chitosan concentration was indicated by an absorbance value measured by UV-vis spectrophotometer (Thermo Scientific, Genesys 10S UV-Vis, USA) at the wavelength of 202 nm. The percentage amount of chitosan impregnated onto the activated carbon was calculated by Eq. (1).

$$\%wt = \frac{(C_0 - C_e)V}{m} \times 100 \quad (1)$$

where %wt is the equilibrium amount of chitosan impregnated onto activated carbon; C_0 and C_e is the initial and equilibrium concentration (g/L) of chitosan in solution; V is the volume (L) of the chitosan solution; m is the weight (g) of activated carbon.

The chitosan impregnated activated carbon (CHI/AC) was oven dried at 378 K for 24 h. The amount of chitosan impregnated on the activated carbon was cross-checked by a calculation of the difference between the weight of chitosan before and after the impregnation process.

2.3 Adsorption analysis

(a) Apparatus

The adsorption experimental set-up (Fig. 2) is comprised of a single stainless steel column with a diameter of 1.9 cm, height of 80 cm and total volume of 200 cm^3 packed containing 160 g of the adsorbent. The column pipeline was made of polyurethane with an outside diameter of 1 cm. The column was equipped with three automatic solenoid valves which were controlled via Visual Basic interface. Two temperature detectors were positioned at the column inlet and outlet to measure any temperature variation due to the adsorption process. Two flowmeters (Dwyer, measuring ranges 0-10 L STP/min and 0-5 L STP/min) was installed at the inlet and outlet to record the flowrate and a pressure gauge (a maximum pressure of 10^3 kPa) was installed at the column to measure the pressure variation. A vacuum pump (30 kPa, GAST Manufacturing Corp., USA) was employed to desorb the gas before and after each experiment.

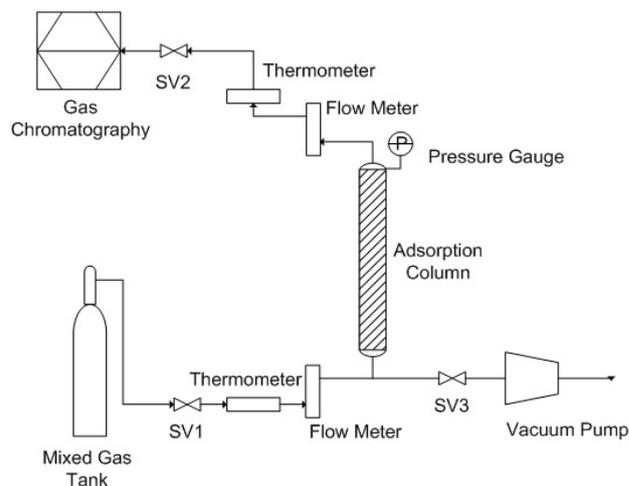


Figure 2. Diagram of the adsorption system.

(b) Dynamic adsorption

The dynamic adsorption was carried out by passing the standard binary gas mixtures (50/50% CO_2/CH_4 , CO_2/H_2 and CO_2/N_2 v/v) through the adsorption column at 298 K. The controlled room temperature was chosen because most of the pressure swing adsorption (PSA) systems were operated at an ambient condition. Before each experiment, the gas was evacuated to 30 kPa by the vacuum pump during the vacuum step. The three-step adsorption cycle was operated: (1) pressurization, (2)

adsorption and (3) depressurization, via three automatic solenoid valves operated according to Table 1. The pressure during the pressurization and adsorption steps was 400 kPa. The feed flow rate during the pressurization step was 2 L STP/min for 2 min. During the adsorption step, the system was holding constant for 15 min to ensure that equilibrium was achieved. During the depressurization, the gas exits at the end of the column and the gas composition was determined by a gas chromatograph (GC) equipped with a thermal conductivity detector (GC-2014; SHIMADZU, Japan), a stainless steel packed column and an argon carrier gas with a flow rate of 50 mL/min. The accuracy of the GC at high CH₄ concentrations was tested with 99.9% CH₄ (Thai Special Gas Co., Ltd.). During the depressurization step, the gas was desorbed by a reduction in pressure from the adsorption pressure to atmospheric pressure. The cycle was repeated until a breakthrough of CO₂ was reached.

Table 1. Valve Operation System.

Valve	SV1	SV2	SV3
Operation			
Pressurization	Open	Close	Close
Adsorption	Close	Close	Close
Depressurization	Close	Open	Close
Vacuum	Close	Close	Open

3. Results and Discussion

In this study, the adsorption dynamics of the activated carbon bed was investigated by using the binary gas mixtures of CO₂/CH₄, CO₂/H₂ and CO₂/N₂ feed (50:50 v/v) to the adsorption column. The adsorption cycle was described in section 2.3 (b) and each cycle lasted approximately for 20 min. A typical pressure profile in the adsorption column for an operating cycle is shown in Fig. 3.

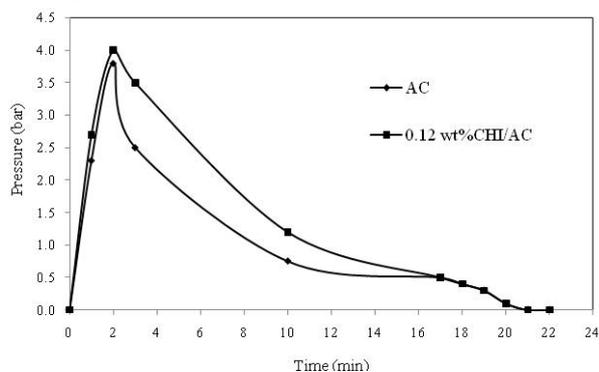



Figure 3. Pressure profile in the adsorption column during CO₂/H₂ dynamic adsorption.

3.1 Biogas upgrading


Biogas is produced by anaerobic digestion, the process in which biomass is converted by microorganisms to biogas under absence of oxygen. Biogas is a mixture of CH₄ 50-70%, CO₂ 30-50% and small traces of N₂, ammonia (NH₃) and hydrogen sulfide (H₂S). Biogas is currently most commonly used for electricity and/or heat production by combined heat and power technology. Upgraded biogas is increasingly used as natural gas substitute in natural gas grids or used as vehicle fuel especially in European and Scandinavian countries [18]. Besides the removal of NH₃ and H₂S, the removal of CO₂ is the main step for upgrading biogas to natural gas quality. Adsorption is one of the widely employed technology for removing CO₂ from biogas and for converting biogas to high purity methane (>96%).

Biogas upgrading was studied using a synthetic mixture of 50-50 (v/v) CH₄/CO₂ mixture. Based on the data on

equilibrium and kinetic selectivity, the 0.76 wt% CHI/AC was selected for dynamic gas separation in comparison with the native activated carbon [19]. When using the native activated carbon as the adsorbent, high purity methane in the range of 93-100% was achieved during cycle 1-2. As the gas separation was processed to cycle 3, the methane purity dropped to the range between 72-84%. The shape of CO₂ concentration profile was broad as shown in Fig. 4 (a). When using the 0.76wt% CHI/AC as the adsorbent, 100% methane was achieved during cycle 1-2. It should be noted that the methane purity can be maintained at 100% during the operating cycle when using the 0.76 wt% CHI/AC, but not by the native activated carbon. The breakthrough of CO₂ occurred at cycle 3 where the methane purity dropped lower to nearly 90%. (Fig. 4 (b)). It is evident that the 0.76 wt% CHI/AC had higher affinity for CO₂, resulting in ultra pure CH₄ as the raffinate, which cannot be achieved by using the native activated carbon.

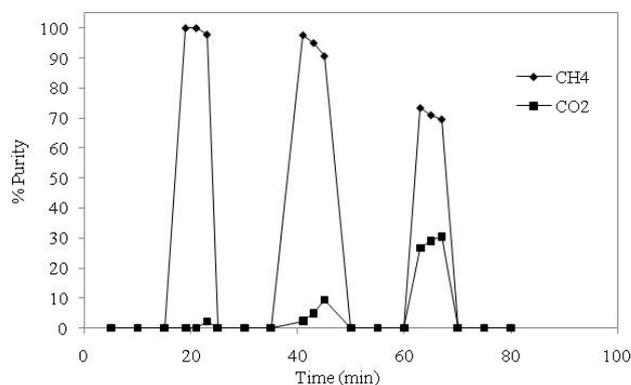

(a) The native activated carbon

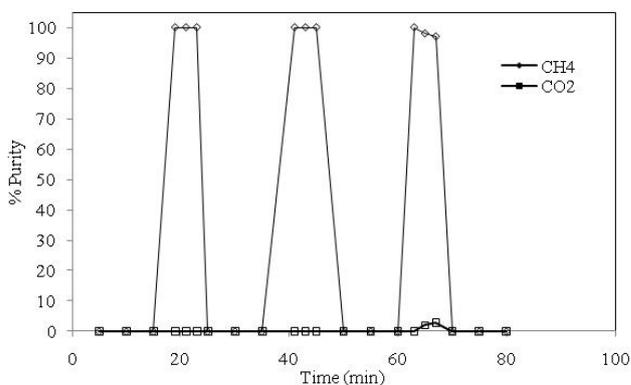

(b) The 0.76 wt% CHI/AC

Figure 4. Dynamic adsorption profile of 50-50 mixture of CO₂/CH₄ (a) the native activated carbon (b) the 0.76 wt% CHI/AC.


3.2 Biohydrogen upgrading

A well known method for hydrogen production is a steam reforming process which yields a gas mixture with a typical composition of H₂ 87%, CO₂ 11%, carbon monoxide (CO) 0.5-1% and CH₄ 1-2%. An alternative hydrogen production is by a biological process which yields a gas mixture with a typical composition of H₂ 50-60% (v/v), CH₄ 10-20%, CO₂ 30-40% and few percentages of water. The separation of carbon dioxide from hydrogen is a necessary step to upgrade biohydrogen. Purified hydrogen can be acquired by a gas separation process such as pressure swing adsorption. There are variety types of adsorbent for the adsorption process. Some of them are available naturally while the others are synthesized such as zeolite, silica gel, activated alumina and activated carbons. Activated carbon has been illustrated to be a potential adsorbent for the separation


of CO₂ from H₂ [20].

Biohydrogen upgrading was studied using a synthetic mixture of 50-50 (v/v) H₂/CO₂ mixture. When using the native activated carbon as the adsorbent, high purity hydrogen in the range of 93-100% was achieved during cycle 1-3. However, during cycle 4-7, the hydrogen purity dropped significantly to the range of 72-84%. The CO₂ concentration increased slowly as shown in Fig. 5 (a).

Based on the data on equilibrium and kinetic selectivity, the 0.12 wt% CHI/AC was selected for dynamic gas separation in comparison with the native activated carbon [21]. When using the 0.12 wt% CHI/AC as the adsorbent, 100% hydrogen was achieved during cycle 1-8, and the breakthrough of CO₂ occurred at cycle 9 with a relatively steep concentration profile as shown in Fig. 5 (b). It is evident that the 0.12 wt% CHI/AC adsorbed CO₂ more effectively, leading not only to the higher H₂ purity in the early cycles, but also the longer effective operating cycles. However, in contrast to physical adsorption of CO₂ onto the native activated carbon, chemisorption is the underlying mechanism for CO₂ adsorption onto the chitosan impregnated activated carbon and desorption of CO₂ from the modified adsorbent requires heat regeneration.

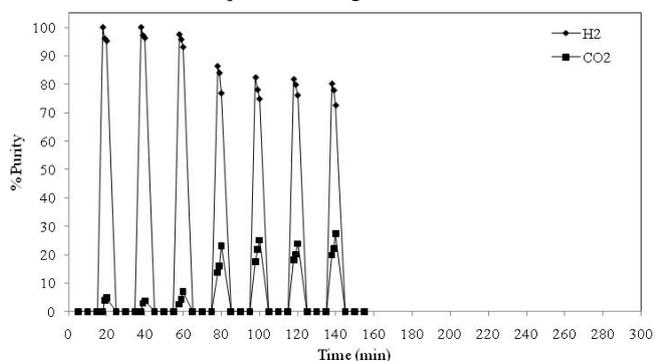

(a) The native activated carbon

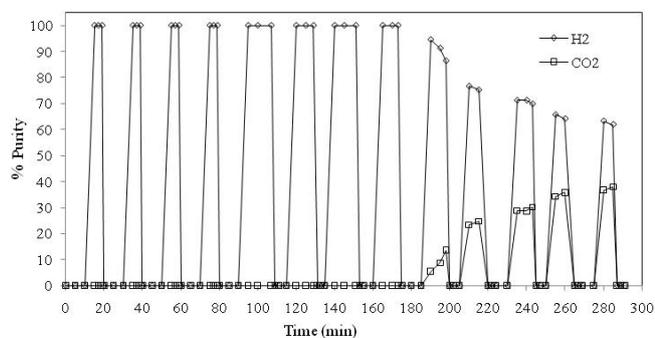

(b) The 0.12 wt% CHI/AC


Figure 5. Dynamic adsorption profile of 50-50 mixture of CO₂/H₂ (a) the native activated carbon (b) the 0.12 wt% CHI/AC.

3.3 CO₂ removal from flue gas


Typical flue gases consist of approximately 17% CO₂, 79% N₂, 4% O₂ and trace amounts of SO₂ and NO_x [22]. Since the beginning of industrial revolution, flue gases have been released to the atmosphere from industries and it has been estimated that the amount of carbon dioxide in the atmosphere increases globally about six billion tones per year [22]. Therefore, one important strategy to reduce CO₂ emission is to recover carbon dioxide from the flue gases.

CO₂ removal from flue gas was studied using a synthetic mixture of 50-50 (v/v) N₂/CO₂ mixture. Activated carbon has been investigated as an adsorbent for the separation of CO₂ from N₂ [23]. Similar to the CO₂/H₂ dynamic adsorption, the CO₂/N₂ dynamic adsorption of the activated carbon yielded ultra pure nitrogen during cycle 1-7. After cycle 7, the nitrogen


purity dropped rapidly to the range between 30-50%. The carbon dioxide concentration increased rapidly with additional operating cycles as shown in Fig. 6 (a). For the CO₂/N₂ dynamic adsorption of 0.12 wt% CHI/AC, 100% nitrogen was achieved for 1-8 cycles. Nitrogen purity dropped 10-15% at cycle 9 (Fig. 6 (b)). For the CO₂/N₂ dynamic adsorption of 0.76 wt% CHI/AC, 100% nitrogen was achieved for 1-9 cycles. Nitrogen purity dropped 40-50% at cycle 10 (Fig. 6 (c)).

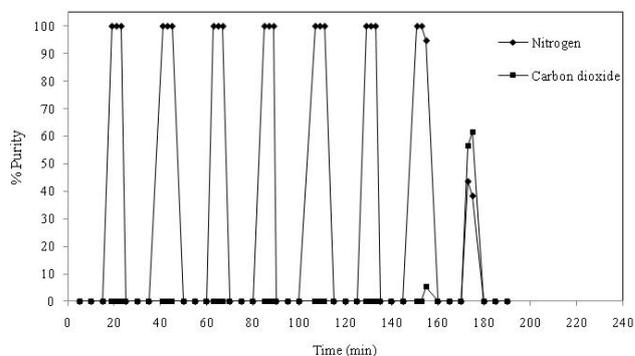

(a) The native activated carbon

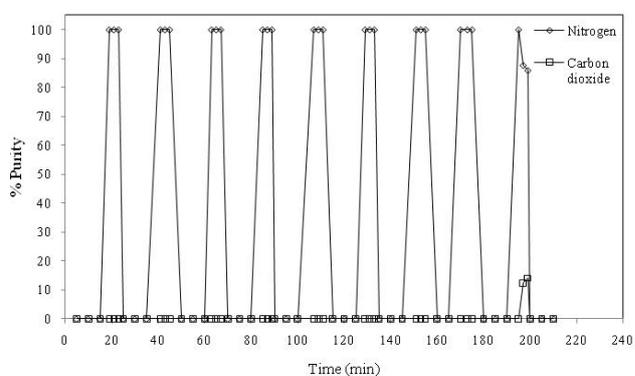

(b) The 0.12 wt% CHI/AC

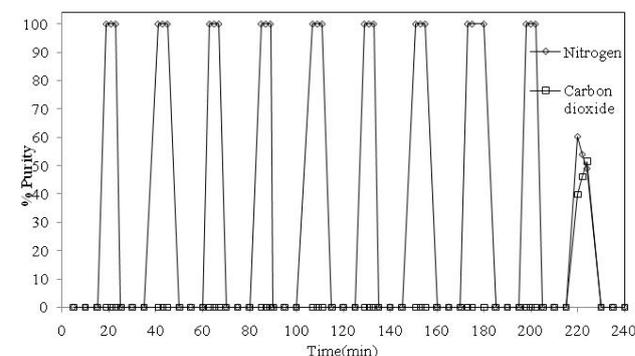

(c) The 0.76 wt% CHI/AC

Figure 6. Dynamic adsorption profile of 50-50 mixture of CO₂/N₂ (a) the native activated carbon (b) the 0.12 wt% CHI/AC (c) the 0.76 wt% CHI/AC

For an integrated process of both gas purification and carbon dioxide capture and storage, regeneration of the adsorbent may not be necessary as the adsorbent also works as carbon storage, but the affinity of an adsorbent for carbon dioxide should be maximized. The modified activated carbon developed in this study would serve this purpose because it has higher adsorption capacity and higher carbon dioxide selectivity compared to the native activated carbon without modification. The storage of CO₂ in adsorbent can reduce the container volume substantially. For example, consider the CO₂ storage at 4 bar and 298 K in a tank volume of 1 m³. Using the ideal gas ($PV = nRT$), the amount of CO₂ in the tank is calculated to be

164 mole. If this amount will be adsorbed on the chitosan impregnated activated carbon, the required amount of the adsorbent is calculated based on the adsorption capacity of 3.76 mole of CO₂ adsorbed per kg to be 43.62 kg (obtained from 164/3.76). Based on the bulk density of the adsorbent (0.59 g/mL or 590 kg/m³), the required volume is estimated to be 0.074 m³. Therefore, when comparing CO₂ storage in a tank with and without containing the modified activated carbon under the same pressure, CO₂ storage on the modified activated carbon can reduce a tank volume by 14 folds.

4. Conclusions

In this study, CO₂ separation from biogas, biohydrogen and flue gas is presented and a combined CO₂ separation and storage is proposed to be a strategy for decreasing the CO₂ concentration in the atmosphere. Dynamic adsorption of 50-50 mixture of CH₄/CO₂ and H₂/CO₂ by the chitosan impregnated activated carbon yielded ultra pure methane and hydrogen, respectively, which cannot be achieved by the native activated carbon. In addition, dynamic adsorption of 50-50 mixture of N₂/CO₂ by the chitosan impregnated activated carbon yielded ultra pure nitrogen. The modified activated carbon has higher adsorption capacity and higher carbon dioxide selectivity compared to the native activated carbon without modification. When comparing CO₂ storage in a tank with and without containing the modified activated carbon under the same pressure, CO₂ storage on the modified activated carbon can reduce a tank volume by 14 folds.

Acknowledgments

The authors would like to acknowledge the National Research Council of Thailand for the research funding (2553A11902006) that made the investment of valuable research units and operations possible. We would like to thank Taming Enterprises Co., Ltd. for providing chitosan samples.

References

- [1] Royer DL, Berner RA, Park J, Climate sensitivity constrained by CO₂ concentrations over the past 420 million years, *Nature* 446 (2007) 530-532.
- [2] Persson M, *Evaluation of upgrading techniques for biogas. Swedish gas center* (2003) Report SGC 142 ISSN 1102-7371.
- [3] Douglas MR, Farooq S, Knaebel KS, *Pressure Swing Adsorption* (1994) VCH, New York, USA.
- [4] Yin CY, Aroua MK, Daud WMAW, Review of modifications of activated carbon for enhancing contaminant uptakes from aqueous solutions, *Sep Purif Technol* 52 (2007) 403-415.
- [5] Liu SX, Chen X, Chen XY, Liu ZF, Wang HL, Activated carbon with excellent Chromium (VI) adsorption performance prepared by acid-base surface modification, *J Hazard Mater* 141 (2007) 315-319.
- [6] Ucer A, Uyanik A, Cay S, Ozkan Y, Immobilisation of tannic acid onto activated carbon to improve Fe(III) adsorption, *Sep Purif Technol* 44 (2005) 11-17.
- [7] Chen JP, Wu S, Chong KH, Surface modification of a granular activated carbon by citric acid for enhancement of copper adsorption, *Carbon* 41 (2003) 1979-1986.
- [8] Zhang Z, Xu M, Wang H, Li Z, Enhancement of CO₂ adsorption on high surface area activated carbon modified by N₂, H₂ and ammonia, *Chem Eng J* 160 (2010) 571-577.
- [9] Garcia AB, Martinez-Alonso A, Leon CAL, Tascon JMD, Modification of the surface properties of an activated carbon by oxygen plasma treatment, *Fuel* 77 (1998) 613-624.
- [10] Xu X, Song C, Andresen JM, Miller BG, Scaroni AW, Novel polyethyleneimine-modified mesoporous molecular sieve of MCM-41 type as high-capacity adsorbent for CO₂ capture, *Energ Fuel* 16 (2002) 1463-1469.
- [11] Xu X, Song C, Andresen JM, Miller BG, Scaroni AW, Preparation and characterization of novel CO₂ "molecular basket" adsorbents based on polymer modified mesoporous molecular sieve MCM-41, *Micropor Mesopor Mater* 62 (2003) 29-45.
- [12] Xu X, Song C, Miller BG, Scaroni AW, Adsorption separation of carbon dioxide from flue gas of natural gas-fired boiler by a novel nanoporous "molecular basket" adsorbent, *Fuel Proc Technol* 86 (2005) 1457-1472.
- [13] Aroua MK, Daud WMAW, Yin CY, Adinata D, Adsorption capacities of carbon dioxide, oxygen, nitrogen and methane on carbon molecular basket derived from polyethyleneimine impregnation on microporous palm shell activated carbon, *Sep Purif Technol* 62 (2008) 611-615.
- [14] Hall GM, Biotechnology approaches to chitin recovery, *Proc. 2nd Asia Pacific Symposium* (1996) Bangkok, Thailand, pp. 26.
- [15] Stevens WF, Chitosan: A key compound in biology and bioprocess technology, *Proc. 2nd Asia Pacific Symposium* (1996) Bangkok, Thailand, pp. 13.
- [16] Stevens WF, (2000) Production of chitin and chitosan: Refinement and sustainability of chemical and biological processing, *Proc. 8th International Chitin and Chitosan Conf. and 4th Asia Pacific Chitin and Chitosan Symposium*, Yamaguchi, Japan, pp. 293.
- [17] Hayes ER, Davies DH, Munroe VG, Organic solvent systems for chitosan, *Proceedings of 1st International Conference on Chitin and Chitosan. MIT Sea Grant Program* (1977) Massachusetts, Edited by Muzzarelli RAA, Pariser ER., pp. 103.
- [18] AEBIOM, European Biomass Association, *A biogas roadmap for Europe* (2009).
- [19] Pitakchon T, Phalakornkule C, The development of adsorbent specific for tertiary gas separation from biogas process, *The 1st EnvironmentAsia International Conference on "Environmental Supporting in Food and Energy Security: Crisis and Opportunity"*, 22-25 March, 2011 (2011) Rama Garden Hotel, Bangkok, Thailand.
- [20] Cao D, Wu J, Modeling the selectivity of activated carbons for efficient separation of hydrogen and carbon dioxide, *Carbon* 43 (2005) 2364-2370.
- [21] Fongchuen J, Phalakornkule C, The development of adsorbent specific for tertiary gas separation from biohydrogen process, *The 1st EnvironmentAsia International Conference on "Environmental Supporting in Food and Energy Security: Crisis and Opportunity"*, 22-25 March, 2011 (2011) Rama Garden Hotel, Bangkok, Thailand.
- [22] Chou CT, Chen CY, Carbon dioxide recovery by vacuum swing adsorption, *Separation and Purification Technology*, 39 (2004) 51-65.
- [23] Dantas TLP, Luna FMT, Silva Jr. II, de Azevedo DCS, Grande CA, Rodrigues AE, Moreira RFP, Carbon dioxide-nitrogen separation through adsorption on activated carbon in a fixed bed, *Chemical Engineering Journal* 169 (2011) 11-19.